

sarbak



TECHNICAL DATA SHEET

CW726R - CuZn36Si1P

GLOBRASS
(PATENTED)
RODS / HOLLOW RODS

Product Code	EN Symbol	EN No	ASTM		Cu	Zn	Pb	Sn	Fe	Ni	Al	Mn	P	Si	Others Total
GLOBRASS	CuZn36Si1P	CW726R	C68370	Min (%)	60,5	Rest	-	-	-	-	-	-	0,01	0,7	-
				Max (%)	64,5	Rest	0,10	0,2	0,2	0,2	-	0,2	0,10	1,3	0,3

(*) Each of the other elements < 0,02 %

Features And Applications

This product is patented lead-free brass. GloBrass is a new material with a copper content close to conventional leaded brass. Machinability and durability are well balanced, thinner bars can be supplied, so it is recommended for the mass production segment where lead-containing brasses are used. GloBrass has excellent cutting machinability, strength, wear resistance and hot malleability. the material complies with ELV, RoHS II and REACH directives.

Area of Usage

It is used in applications such as automotive parts, electrical parts and faucet parts etc.

Range of Products

Cold drawn and extruded bars, coils and hollow bars are produced in our extrusion and cold drawing department. Please enquire about suitable forms, dimensions and mechanical properties.


TECHNICAL SPECIFICATIONS

Structure	kappa+gama	Melting Point	860-925 °C
Machinability	%80	Hot Forming	580-650 °C
Density	8,25 g/cm ³	Soft Annealing	550-650 °C
Electrical Conductivity	16 %IACS	Soft Annealing Time	1-3 Hours
Thermal Conductivity	73 W/(m.K)	Stress Relieving	200-300 °C
Elasticity Module	100 GPa	Stress Relieving Time	1-3 Hours
Coeff. of Thermal Expansion	19 10 ⁻⁶ /K	Max. Depth of Dezincification	-

INDICATIVE SHAPED ENDS DIMENSIONS

Nominal Diameter or Width		Type A - Chamfer Length (L)		Type B - Point Length (L)	
Over	Up to and including	Min (mm)	Max (mm)	Min (mm)	Max (mm)
8	10	0,2	1,5	2	7
10	20	0,2	2	3	10
20	30	0,2	3	4	12

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

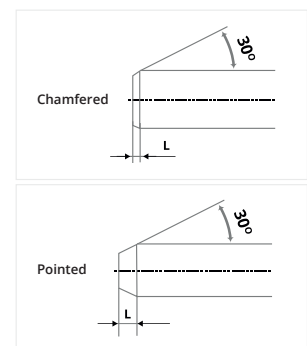



CW726R-CuZn36Si1P

Nominal Diameter or Width Across-flats (mm)		Preferred (available) Lengths (mm)	Tolerance on Length (mm)
Over	Up to and including		
8 ^{inc.}	30	3.000-4.000	±50
30	65	3.000-4.000	±100

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment
Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

Material Condition	Nominal Diameter (mm)		Width Across-Flats (mm)		Tensile Strength Rm N/mm ² (MPa)	0,2 % Proof Strength N/mm ² (MPa)		Elongation			Hardness (HBW)	
	Over	Up to and inc	Over	Up to and inc		Min	Min	Max	A100mm (%)	A11,3 (%)	A (%)	Max
					Min				Min	Min		
M	All		All		As manufactured							
R450	8	65	8	65	450	-	400	-	-	15	-	-
H090	8	65	8	65	-	-	-	-	-	-	90	180
R480	8	40	15	40	480	260	-	-	-	12	-	-
H120	8	40	15	40	-	-	-	-	-	-	120	210
R540	8	20	8	15	540	400	-	-	2	3	-	-
H150	8	20	8	15	-	-	-	-	-	-	150	220

EN 12168 - Hollow Rods for Free Machining

Material Condition	Wall Thickness (mm)		Tensile Strength Rm N/mm ² (MPa)	0,2 % Proof Strength N/mm ² (MPa)		Elongation A (%)	Hardness (HBW)		Hardness (HV)	
				Min	Min		Max	Min	Max	Min
			Min			Max				
M	All		As manufactured							
R460	4	20	460	-	410	15	-	-	-	-
H100	4	20	-	-	-	-	100	180	100	190
R510	4	20	510	270	-	10	-	-	-	-
H130	4	20	-	-	-	-	130	210	130	220
R580	4	7	580	420	-	3	-	-	-	-
H150	4	7	-	-	-	-	150	-	160	-

EN 12165 - Wrought and Unwrought Forging Stocks

Material Condition	Nominal Diameter (mm)		Hardness (HBW)	
	Over	Up to and inc	Min	Max
M	All		As manufactured	
H130	10	65	130	220

STANDARD		EN 12164			EN 12165		EN 12168				
Dimension Range		Round Rod		Hexagonal, Square	Round Rod		Round and Hexagonal Hollow Rod, Outer Dim. Tol.		Hole Tolerance Round		Hole Tol. Hexagonal
Over	Up to & inc.	Class A	Class B	Rod	Class A	Class B	Class A	Class B	Class A	Class B	-
8	10	0 -0,06	0 -0,036	0 -0,09	±0,25	±0,14	-	-	-	-	-
10	13	0 -0,07	0 -0,043	0 -0,11	±0,25	±0,14	-	-	-	-	-
13	18	0 -0,07	0 -0,043	0 -0,11	±0,25	±0,14	-	-	±0,35	-	+0,70 -0
18	20	0 -0,08	0 -0,052	0 -0,13	±0,30	±0,17	-	-	±0,42	-	+0,84 -0
20	23	0 -0,08	0 -0,052	0 -0,13	±0,30	±0,17	-	0 -0,21	±0,42	-	+0,84 -0
23	26	0 -0,08	0 -0,052	0 -0,13	±0,30	±0,17	-	0 -0,21	±0,42	-	+0,84 -0
26	30	0 -0,08	0 -0,052	0 -0,13	±0,30	±0,17	-	0 -0,21	±0,42	-	+0,84 -0
30	50	0 -0,16	-	0 -0,16	±0,60	±0,20	-	0 -0,25	±0,80	-	+1,6 -0
50	55	0 -0,19	-	0 -0,19	±0,70	±0,37	-	0 -0,46	±0,95	-	-
55	65	0 -0,19	-	-	±0,70	±0,37	±0,60	0 -0,46	±0,95	-	-
65	80	-	-	-	±0,70	-	±0,60	0 -0,46	-	-	-
80	110	-	-	-	±2	-	-	-	-	-	-

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity: %8 (max).

Minimum wall thickness is 5 mm over 65 mm.


"For hollows, maximum outer diameter is Ø78 mm and maximum producible weight is 28 kg in 1 meter."

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance

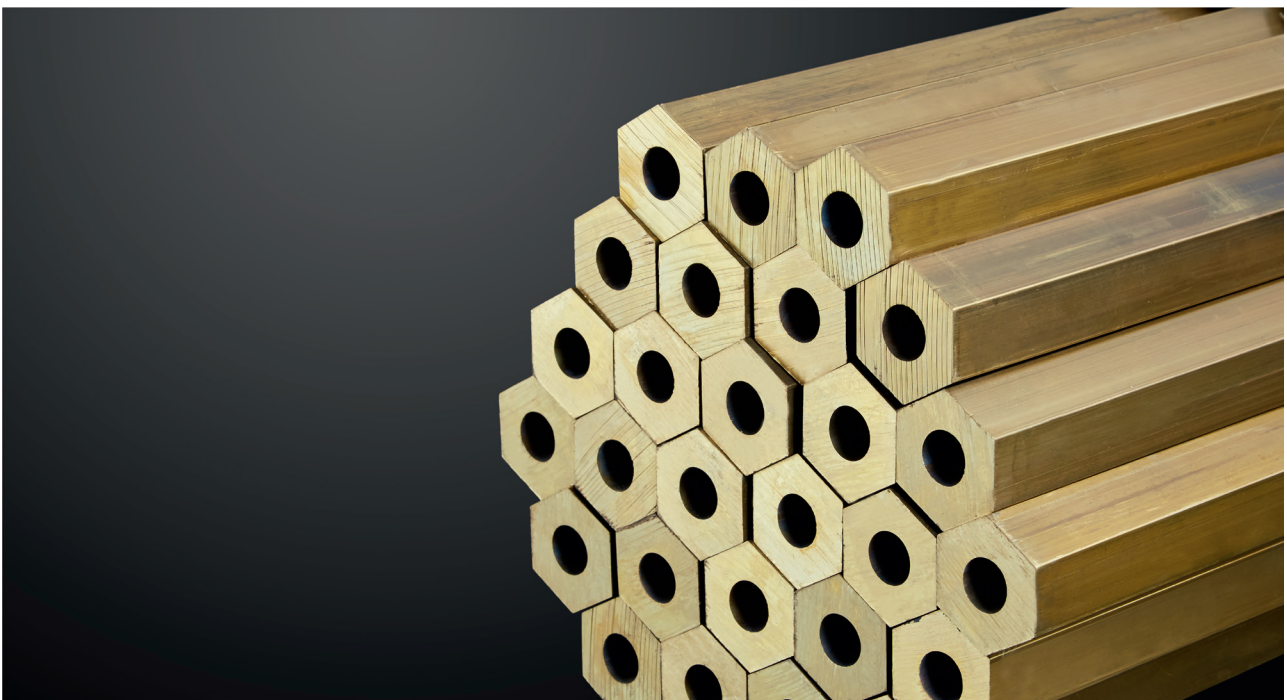



Headquarter

SARBAK METAL TİC. ve SAN. A.Ş.
Eğitim Mah. Adım Sok. Oran İş Merkezi No: 10 -18 Kat: 3 Daire No: 39 - 49 34722
Hasanpaşa / Kadıköy / İstanbul / Türkiye
T: +90 216 414 45 35 pbx | F: +90 216 414 45 40

Factory

Çerkezköy Organize Sanayi Bölgesi Gazi Osman Paşa Mah. 8.Cad. No: 3 59500
Çerkezköy / Tekirdağ / Türkiye
T: +90 282 725 19 60 pbx | F: +90 282 725 19 70